Nittoseiko Analytech



Sheet No.

AQF MR 026E Materials

Determination of chlorine in pigment

1/2

Instruments : AQF-2100H System,HF-210,GA-210,ABC-210/ASC240S

Method : Combustion-ion chromatography

Related standard:

It is critically important to know the chlorine content in the sample for quality control. Concentrations of fluorine, chlorine, bromine, iodine, and sulfur can be determined and accurately by using a combustion ion chromatography (CIC) system combining an Automatic Quick Furnace Model AQF-2100H which safely combusts samples with an ion chromatograph.

0	D'annert					
Sample name	Pigment					
Sample status						
Measuring items	Chlorine (CI)					
Measurement	Sample is thermally decomposed in argon (Ar) atmosphere, then combusted in oxygen					
principle	(O ₂) atmosphere. Halogens in the sample are converted to hydrogen halide and					
	halogen gas and sulfur turns into sulfur oxide. These components are collected into					
	absorbing solution and converted to halide ion and sulfate ion. The resulting solution is					
	analyzed by injecting into an ion chromatograph (IC).					
	Analyzing flow					
	[Sample weighing]→[Combustion]→[Collection of combustion gas]→[IC analysis]					
Parameters	1. AQF-2100H					
	Sample size : 80mg					
	Sample boat : Ceramic sample boat, SXSMBS					
	Additive: WO ₃ 100mg					
	Pyrolysis tube: Quartz tube filled with quartz wool					
	Absorbent: Hydrogen peroxide / water					
	HF-210 Heater Temp. Inlet: 1000degC					
	Outlet: 1100degC					
	Gas flow Ar : 200 ml/min					
	O ₂ : 400 ml/min					
	GA-210 Absorbent volume : 5ml					
	Sampling loop: 100 ul					
	Absorption tube: For 10 ml					
	Water supply : 2					
	Ar flow for water supply : 100 ml/min					

Nittoseiko Analytech



Sheet No.

AQF MR 026E Determination of chlorine in pigment

2/2

2. Ion chromatograph

Ion chromatograph : DIONEX ICS-1500


Column : DIONEX Ion Pack AG12A / Ion Pack AS12A

Eluent : 2.7mM Na₂CO₃ / 0.3mM NaHCO₃

Eluent flow : 1.50ml / min
Detector : Conductivity
Suppressor : ASRS-4-mm
Measuring time : 30min

Sampling loop : 100 μ l using GA-210 sampling loop Calibration : F Cl Br S :0.1ppm \sim 10ppm

Results Chromatogram

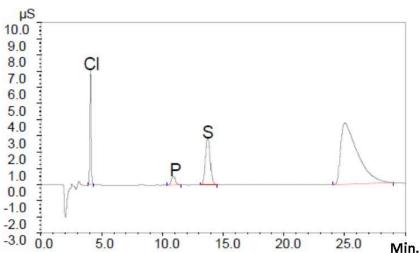

Results

CI	1st	2nd	3rd	Average(ppm)	RSD(%)
Pigment 1	222	226	234	227	2.6
Pigment 2	62.7	64.0	65.3	64.0	2.0

Remarks

*Handling of reagents: Confirm labels and safety data sheets of reagents and handle them with enough care.

*Automation is possible by using an Automatic Sample Changer, ASC-240S.

When ASC-240S is used, the boat to be used will be a ceramic boat, TX3SCX.

AQF2100H_11_010E

^{*}This application sheet is provided as reference, and does not assure the measurement results. Please consider analysis environment, external factors and sample nature for optimal conditions before the measurement.